

Effects of Culturing Factors and Reaction Conditions on the Synthesis of Gold Nanoparticles by Four Enterobacterial Species



Pongrawee Nimnoi¹ and Neelawan Pongsilp^{2,*}

¹Microbiology Division, Department of Science and Bioinnovation, Faculty of Liberal Arts and Science, Kasetsart University - Kamphaeng Saen Campus, Nakhon Pathom, Thailand

²Department of Microbiology, Faculty of Science, Silpakorn University, Nakhon Pathom, Thailand

Abstract:

Introduction: Synthesis of gold nanoparticles (AuNPs) using enterobacteria confers many advantages, but the efficiency depends on the bacterial strains and culture conditions. Therefore, the selection of the most effective strains and the optimization of the culturing factors and reaction conditions are required.

Methods: Gold resistance and AuNP synthesis were evaluated across 105 enterobacterial strains. The AuNPs synthesized by the four selected strains were characterized using scanning electron microscopy (SEM). AuNP synthesis was improved by optimizing several parameters, including culture media, inducer concentrations, aeration, cultivation times, reaction temperatures, and incubation times.

Results: Fifty-six strains synthesized AuNPs at concentrations ranging from 7.56 ± 0.28 to 77.92 ± 3.92 $\mu\text{g/mL}$. The AuNPs synthesized by the four selected strains, including *Citrobacter freundii* ENTSE 1-3, *Enterobacter cloacae* ENTSE 8-1, *Hafnia alvei* ENTSE 15-1, and *Morganella morganii* SFTCBS1, appeared spherical to slightly polyhedral, with average sizes ranging from 22 to 28 nm. Lennox Luria-Bertani (LB) medium and static conditions were favourable culturing parameters for AuNP synthesis by all four strains. The most favourable reaction conditions varied among the four strains as follows: *C. freundii* ENTSE 1-3 (at 37°C for 72 h and 120 h); *E. cloacae* ENTSE 8-1 (at 55°C for 72 h and 120 h); *H. alvei* ENTSE 15-1 (at 37°C for 72 h and 120 h, as well as at 55°C for 24 h and 48 h); and *M. morganii* SFTCBS1 (at 55°C for 120 h).

Discussion: AuNP synthesis by the four selected strains offers several advantages, including a simple growth medium, a short cultivation time, a rapid reaction, convenient product harvesting, stable AuNPs, and no requirement for extra equipment.

Conclusion: This study determined the most suitable cultivation and reaction conditions to enhance the yield of AuNPs.

Keywords: Gold nanoparticle (AuNP), Enterobacteria, Culturing factor, *Citrobacter freundii*, *Enterobacter cloacae*, *Hafnia alvei*, *Morganella morganii*.

© 2026 The Author(s). Published by Bentham Open.

This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International Public License (CC-BY 4.0), a copy of which is available at: <https://creativecommons.org/licenses/by/4.0/legalcode>. This license permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

*Address correspondence to this author at the Department of Microbiology, Faculty of Science, Silpakorn University, Nakhon Pathom, Thailand; E-mail: pongsilp_n@su.ac.th

*These authors contributed equally to this work and share first authorship.

Cite as: Nimnoi P, Pongsilp N. Effects of Culturing Factors and Reaction Conditions on the Synthesis of Gold Nanoparticles by Four Enterobacterial Species. Open Microbiol J, 2026; 20: e18742858487205. <http://dx.doi.org/10.2174/0118742858487205260717093037>



CrossMark

Received: February 23, 2026

Revised: April 24, 2026

Accepted: May 08, 2026

Published: July 22, 2026



Send Orders for Reprints to reprints@benthamscience.net

1. INTRODUCTION

Gold nanoparticles (AuNPs) are of great interest due to their unique and promising properties, including

inertness, stability, biological activity, biocompatibility, high binding affinity, low toxicity, cell membrane penetration ability, apoptosis induction ability, interaction with light via surface plasmon resonance (SPR), optical

properties, and electrical properties. AuNPs have been employed in a vast array of applications across multiple fields. AuNPs have been utilized in the detection of various biomolecules. In the medical field, AuNPs have been applied in diagnostics, anticancer therapy, photothermal therapy (PTT), photodynamic therapy (PDT), radiation therapy (RT), gene therapy, and immunotherapy. AuNPs have demonstrated therapeutic potential in antimicrobial, antidiabetic, antioxidant, and anti-inflammatory treatments. AuNPs have also been employed as carriers for drugs, antibiotics, nucleic acids, and proteins. In imaging processes, AuNPs have been used in X-ray photography and computed tomography (CT). In the agricultural field, AuNPs have been shown to promote plant growth and induce seed germination. In environmental applications, AuNPs have been used for air cleaning and water purification [1-3].

AuNPs display a variety of morphologies, encompassing differences in shape (*e.g.* sphere, oval, rod, cube, cage, shell, wire, branch, star, flower, bipyramid, triangle, pentagon, hexagon, and cluster) [2-4], size (approximately 2 to 200 nm) [2, 3], and colour (*e.g.* red, orange, brown, purple, and blue) [5]. The morphologies of AuNPs are crucial to their properties, including specificity, toxicity, cellular uptake ability, and cell membrane penetration ability [4]. The factors determining AuNP morphology include medium pH, reaction pH, temperature, time, metal salt concentration, trisodium citrate ($\text{Na}_3\text{C}_6\text{H}_5\text{O}_7$) concentration, and the ratio of trisodium citrate to chloroauric acid (HAuCl_4) [2, 4, 6-8]. The reaction rates have been reported to be influenced by pH, temperature, salt concentration, and HAuCl_4 concentration [2, 9].

Various approaches to generating AuNPs are categorized into three types: physical, chemical, and biological processes. Green technologies have increasingly gained popularity because of their advantages, including safety, eco-friendliness, high energy efficiency, product stability, and the avoidance of high temperatures and harsh chemicals. Numerous bacteria, fungi, yeasts, and algae have been successfully employed in the green synthesis of AuNPs.

Bacterial synthesis offers advantages because some bacteria are not affected by the presence of heavy metals, and their extracellular synthesis facilitates the purification process [2, 10]. The ability to synthesize AuNPs has been reported in various groups of bacteria as follows: (1) enterobacteria (*e.g.* *C. freundii*, *Enterobacter xiangfangensis*, *Escherichia coli*, *Klebsiella pneumoniae*, *Proteus mirabilis*, and *Serratia marcescens*) [11-16]; (2) marine bacteria (*e.g.* *Bacillus marisflavi*, *Lysinibacillus odyseyi*, *Shewanella oneidensis*, and *Vibrio alginolyticus*) [17-21]; (3) actinobacteria (*e.g.* *Rhodococcus* spp. and *Streptomyces* spp.) [22, 23]; (4) lactic acid bacteria (*e.g.* *Lactobacillus acidophilus*, *Lactobacillus casei*, and *Streptococcus thermophilus*) [9, 24]; and (5) other bacteria (*e.g.* *Bacillus licheniformis*, *Bacillus subtilis*, *Pseudomonas aeruginosa*, and *Pseudomonas fluorescens*) [9, 17, 25-28]. AuNP synthesis using enterobacteria

confers the advantages of ease, rapidity, environmental friendliness, cost-efficiency, product uniformity, and feasibility for large-scale production [29, 30].

Due to the prominent ability of enterobacteria and their advantages in AuNP synthesis, this study was conducted to select the most effective strains, optimize the culturing factors and reaction conditions to maximize the yield of AuNPs synthesized by four enterobacterial species, and characterize the synthesized AuNPs using scanning electron microscopy (SEM).

2. MATERIALS AND METHODS

2.1. Enterobacterial Strains

A collection of 105 enterobacterial strains was established in our previous studies through the isolation of bacteria from 15 types of fresh seafood sourced in Thailand. All strains were identified to the genus level based on the sequence similarity of the 16S rRNA gene. Twenty-four strains were identified to the species level according to the VITEK 2 system. All strains were classified into nine genera: *Citrobacter* (20 strains), *Enterobacter* (55 strains), *Hafnia* (two strains), *Klebsiella* (six strains), *Morganella* (four strains), *Providencia* (12 strains), *Salmonella* (two strains), *Serratia* (two strains), and *Yersinia* (two strains) [31, 32].

2.2. Assessment of Gold Resistance Among 105 Enterobacterial Strains

The inocula, prepared by overnight cultivation of the strains in Lennox Luria-Bertani (LB) broth, were subcultured into Mueller-Hinton (MH) broth (Sigma-Aldrich, St. Louis, MO, USA) containing filter-sterilized $\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$ at concentrations of 19.5 mg/L (50 μM), 39 mg/L (100 μM), and 58.5 mg/L (150 μM) to obtain an initial concentration of 1.00×10^5 colony-forming units (CFU)/mL. The bacterial cultures were grown at 37°C for 24 h. Turbidity and an optical density at 600 nm (OD_{600}) above 0.1 indicated bacterial growth and, hence, gold resistance.

2.3. Determination of Concentrations of AuNPs Synthesized by 105 Enterobacterial Strains

The methodology for assessing AuNP synthesis was modified from the previously reported protocol [33]. The strains were cultivated in Lennox LB broth at 37°C for 36 h under static conditions. The cell-free supernatants were obtained by centrifugation of the cultures at 11,000 rpm for 10 min at 4°C in an Eppendorf 5804R centrifuge (Eppendorf, Selangor Darul Ehsan, Malaysia). The reaction mixtures were prepared by mixing 10 mL of supernatant with 10 mL of 1 mM HAuCl_4 and then incubating the mixtures undisturbed at 37°C for 24 h and 120 h in the dark. The negative control was prepared using uninoculated medium instead of cell-free supernatant and served as a blank in the spectrophotometric method for determining AuNP concentration. AuNP synthesis was indicated by the colour changes of the reaction mixtures from light yellow to a

diverse range of colours, including red, orange, brown, purple, and blue. The final colours were determined by the size, shape, and aggregation of the AuNPs [5, 10]. The ultraviolet-visible (UV-vis) spectra of the synthesized AuNPs were scanned using a NanoDrop 2000C spectrophotometer (Thermo Scientific, Waltham, MA, USA). The optical densities (ODs) at $\lambda_{\max}$ of the reaction mixtures were quantified using a Cecil CE1011 spectrophotometer (Cecil Instruments, Cambridge, UK). A commercial AuNP suspension (Sigma-Aldrich, St. Louis, MO, USA) with the same $\lambda_{\max}$ as the synthesized AuNPs was used for concentration quantification. A commercial AuNP suspension with an OD of 1.0 and a concentration of 35 $\mu\text{g/mL}$ was serially diluted in Lennox LB medium to obtain concentrations ranging from 5 to 35 $\mu\text{g/mL}$. Lennox LB medium served as a blank in the spectrophotometric method. The OD was measured for each AuNP concentration. A standard curve was plotted using the OD values and AuNP concentrations. The concentrations of the synthesized AuNPs were quantified using the standard curve. All reactions were performed in triplicate.

2.4. Species Identification of the Selected Strains According to the VITEK 2 System

Enterobacterial strains from four genera were selected based on their highest concentrations of AuNPs synthesized. The selected strains were subjected to species identification using the Gram-Negative (GN) card of the VITEK 2 system version 07.01 (bioMérieux, Inc., Durham, NC, USA).

2.5. SEM Imaging of the Synthesized AuNPs

The reaction mixtures of the four selected strains were filtered through 0.45- μm pore size membranes (Sartorius Stedim Biotech, Gottingen, Germany). The filtrates were centrifuged at 11,000 rpm for 10 min at 4°C in an Eppendorf 5804R centrifuge (Eppendorf, Selangor Darul Ehsan, Malaysia) to obtain AuNP pellets. The AuNP pellets were washed three times and then dissolved in sterile ultrapure water (Invitrogen, Waltham, MA, USA). The morphologies of the synthesized AuNPs were characterized by Tescan Mira3 SEM (Tescan Orsay Holding, Brno-Kohoutovice, Czech Republic). The shapes and sizes of the synthesized AuNPs were analyzed with ImageJ software [34].

2.6. Determination of the Effects of Culturing Factors and Reaction Conditions on AuNP Synthesis by the Selected Strains

The inocula were prepared by cultivating the four selected strains in Lennox LB broth at 37°C for 36 h with shaking at 150 rpm. The inocula were adjusted to an initial concentration of 1.00×10^5 CFU/mL for cultivation under conditions with varied culturing factors. The culturing factors were as follows: (1) culture media including Lennox LB (pH 7.0 ± 0.2) [35], brain heart infusion (BHI) (pH 7.4 ± 0.2) (Scharlab, Barcelona, Spain), and minimal medium M63 (pH 7.3 ± 0.2) [36]; (2) inducer concentrations (0, 20, and 50 μM HAuCl₄); (3) static and aerated conditions (without shaking and with shaking at

150 rpm, respectively); and (4) cultivation times (6, 12, 24, 36, and 48 h). The varied reaction conditions were combinations of incubation temperatures (37°C and 55°C) and times (6, 24, 48, 72, and 120 h). Negative controls were performed using uninoculated media with the same concentrations of HAuCl₄, rather than cell-free supernatants. These controls also served as blanks in the spectrophotometric method for determining AuNP concentration under each relevant condition. The AuNP concentrations were determined, as mentioned earlier.

2.7. Statistical Analysis

Data were analyzed using SPSS software version 19.0 (IBM Corp., Chicago, IL, USA). All experiments were performed in triplicate ($n = 3$). Results are expressed as the means $\pm$ standard deviations (SDs), supplemented by 95% confidence intervals (CIs). Significant differences among means were assessed using one-way or two-way analysis of variance (ANOVA), followed by Tukey's HSD post hoc test for multiple comparisons. The magnitude of effects was quantified using partial eta squared (η_p^2). A p -value < 0.05 was considered statistically significant. ANOVA summary outputs, including sums of squares, degrees of freedom (df), and F -statistics, were computed.

3. RESULTS

3.1. Gold Resistance Among 105 Enterobacterial Strains

Of the 105 enterobacterial strains screened for resistance to a gold compound, HAuCl₄, 31 (29.5%), 7 (6.7%), and 11 (10.5%) strains were resistant at maximum concentrations of 50, 100, and 150 μM , respectively.

3.2. AuNP Synthesis by 105 Enterobacterial Strains

AuNP synthesis could be perceived from the color changes of the reaction mixtures from light-yellow to a diverse range of colors, including red, orange, brown, purple, and blue [5, 10]. These color changes were observed for 56 strains (53.3%). The color changes of the reaction mixtures due to the AuNP synthesis are shown in Fig. (1). The AuNP-producing bacteria were distributed in eight genera, including *Enterobacter* (29 strains), *Citrobacter* (nine strains), *Providencia* (seven strains), *Klebsiella* (three strains), *Morganella* (three strains), *Serratia* (two strains), *Yersinia* (two strains), and *Hafnia* (one strain). Fifty-six AuNP-producing strains synthesized extracellular AuNPs at concentrations ranging from 7.56 ± 0.28 to 77.92 ± 3.92 $\mu\text{g/mL}$. When comparing reaction incubation times of 24 h and 120 h, AuNP formation was observed in 34 strains at 120 h and in 22 strains at the earlier time point of 24 h. The four representative strains producing the highest AuNP concentrations within each genus were selected for further studies. The four selected strains and their concentrations of the synthesized AuNPs were *Citrobacter* sp. ENTSE 1-3 (56.64 ± 1.95 $\mu\text{g/mL}$), *Enterobacter* sp. ENTSE 8-1 (56.00 ± 3.84 $\mu\text{g/mL}$), *Hafnia* sp. ENTSE 15-1 (30.16 ± 1.68 $\mu\text{g/mL}$), and *Morganella morganii* SFTCBS1 (77.92 ± 3.92 $\mu\text{g/mL}$). All four strains synthesized AuNPs with a purple-red color and a $\lambda_{\max}$ of 540 nm.

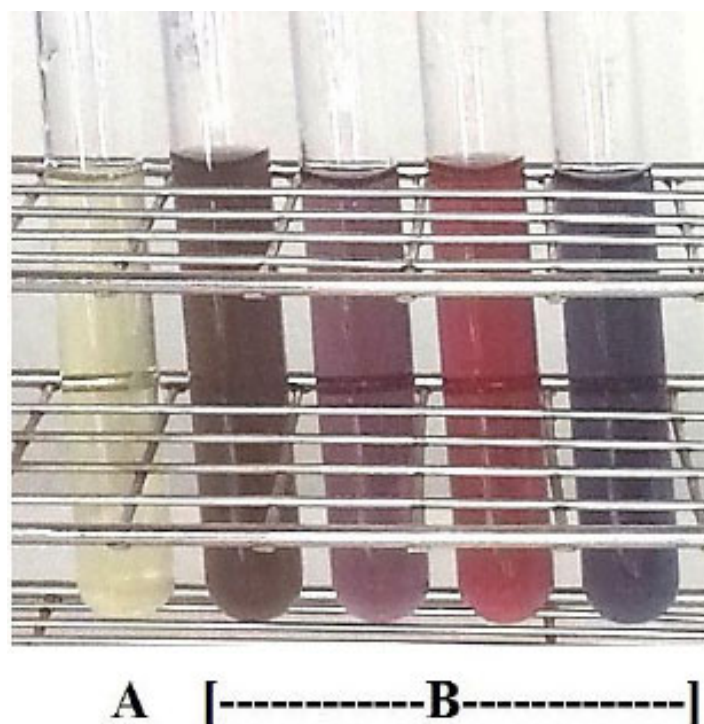


Fig. (1). Color changes of reaction mixtures resulting from AuNP synthesis. The initial color of the reaction mixture was light yellow (A), and the final colors of the reaction mixtures containing AuNPs were brown, violet, red, and purple (B).

3.3. Species Identification of the Selected Strains According to the VITEK 2 System

Citrobacter sp. ENTSE 1-3, *Enterobacter* sp. ENTSE 8-1, and *Hafnia* sp. ENTSE 15-1 were previously identified at the genus level based on the alignment of partial 16S rRNA gene sequences [32]. These three strains were identified to the species level based on the VITEK 2 system as *Citrobacter freundii* ENTSE 1-3, *Enterobacter cloacae* subsp. *cloacae* ENTSE 8-1, and *Hafnia alvei* ENTSE 15-1, each with a probability of 99%. *Morganella morganii* subsp. *sibirica* SFTCBS1 was identified with a 99% probability using the VITEK 2 system in the previous study [31].

3.4. SEM Images of the Synthesized AuNPs

The SEM images (Fig. 2) depict the shapes and sizes of the AuNPs synthesized by four enterobacterial species. The synthesized AuNPs possessed spherical to slightly polyhedral shapes. The average sizes of the AuNPs synthesized by each strain were as follows: *C. freundii* ENTSE 1-3 (26.8 ± 14.4 nm); *E. cloacae* ENTSE 8-1 (27.8 ± 15.0 nm); *H. alvei* ENTSE 15-1 (22.1 ± 13.0 nm); and *M. morganii* SFTCBS1 (22.3 ± 13.2 nm).

3.5. Cultivation and Reaction Conditions Optimized for AuNP Synthesis by the Selected Strains

Factors promoting AuNP synthesis, including culture media, inducer concentrations, aeration, cultivation times, reaction temperatures, and incubation times, were

optimized for the four selected strains. To evaluate the effect of culture media, the inocula of selected strains were grown in three culture media at 37°C for 36 h under static conditions. The AuNP concentrations were determined, as mentioned earlier. The concentrations of AuNPs synthesized by all four strains grown in three culture media are presented in Table 1. At both incubation times (24 h and 120 h), the AuNP concentrations were significantly highest for all four strains grown in Lennox LB.

To evaluate the effect of HAuCl₄ as an inducer, the inocula of the selected strains were grown in Lennox LB broth without and with HAuCl₄ at concentrations of 20 and 50 µM at 37°C for 36 h under static conditions. The AuNP concentrations were determined as mentioned earlier. The concentrations of AuNPs synthesized by all four strains grown in the absence and presence of HAuCl₄ are presented in Table 2. The effect varied depending on the strain. The presence of 20 µM HAuCl₄ yielded the significantly highest AuNP concentration from *C. freundii* ENTSE 1-3 at an incubation time of 120 h. The presence of 50 µM HAuCl₄ yielded the significantly highest AuNP concentration from *E. cloacae* ENTSE 8-1 at an incubation time of 120 h. *H. alvei* ENTSE 15-1 did not resist 20 or 50 µM HAuCl₄; hence, HAuCl₄ could not promote AuNP synthesis by this strain. Although *M. morganii* SFTCBS1 resisted 20 and 50 µM HAuCl₄, HAuCl₄ was unable to promote AuNP synthesis by this strain.

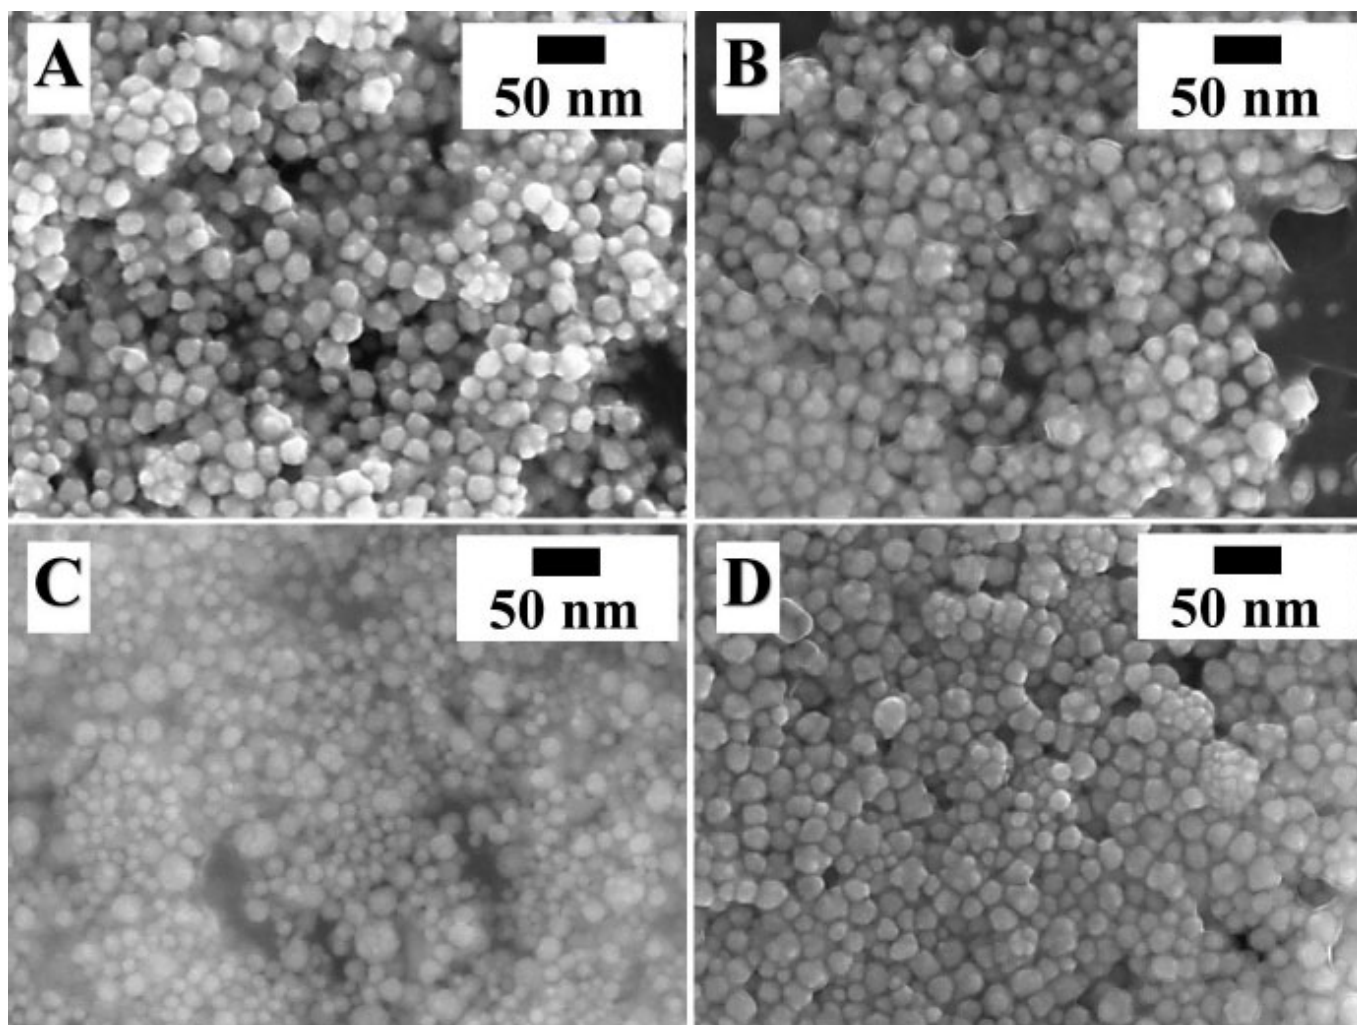


Fig. (2). SEM images of AuNPs synthesized by enterobacterial strains. Spherical to slightly polyhedral AuNPs with average sizes ranging from 22 to 28 nm were synthesized by *C. freundii* ENTSE 1-3 (A), *E. cloacae* ENTSE 8-1 (B), *H. alvei* ENTSE 15-1 (C), and *M. organii* SFTCBS1 (D).

Table 1. AuNP concentrations obtained from the four selected strains grown in three culture media.

Bacterial Strain	Culture Medium	Reaction Incubation time (h)	AuNP Concentration ($\mu\text{g/mL}$) from a Culture Grown in Culture Medium (mean $\pm$ SD)	95% Confidence Interval (CI)	Effect Size (η_p^2)	p-value
<i>C. freundii</i> ENTSE 1-3	Lennox LB	24	38.12 ± 1.29^a	[35.02, 41.23]	0.99	< 0.001
		120	57.09 ± 2.42^k	[51.07, 63.11]	0.99	0.001
<i>E. cloacae</i> ENTSE 8-1	Lennox LB	24	54.90 ± 2.86^{ijk}	[47.78, 62.03]	0.99	0.001
		120	51.41 ± 0.69^j	[49.67, 53.14]	0.99	< 0.001
<i>H. alvei</i> ENTSE 15-1	Lennox LB	24	12.28 ± 0.88^f	[10.08, 14.47]	0.99	0.002
		120	29.69 ± 0.76^{gf}	[27.79, 31.59]	0.99	< 0.001
<i>M. organii</i> SFTCBS1	Lennox LB	24	76.85 ± 2.61^i	[70.34, 83.36]	0.99	< 0.001
		120	74.02 ± 2.35^i	[68.18, 79.86]	0.99	< 0.001
<i>C. freundii</i> ENTSE 1-3	BHI	24	0.33 ± 0.50^a	[-0.93, 1.59]	0.62	0.375
		120	0.05 ± 0.09^a	[-0.18, 0.30]	0.57	0.423

Bacterial Strain	Culture Medium	Reaction Incubation time (h)	AuNP Concentration ($\mu\text{g/mL}$) from a Culture Grown in Culture Medium (mean $\pm$ SD)	95% Confidence Interval (CI)	Effect Size (η_p^2)	p-value
<i>E. cloacae</i> ENTSE 8-1	BHI	24	11.13 ± 0.18^f	[10.66, 11.60]	0.99	< 0.001
		120	8.76 ± 0.62^{ef}	[7.21, 10.30]	0.99	0.002
<i>H. alvei</i> ENTSE 15-1	BHI	24	5.52 ± 1.03^{cde}	[2.94, 8.09]	0.98	0.012
		120	0.05 ± 0.09^a	[-1.76, 0.28]	0.57	0.423
<i>M. morganii</i> SFTCBS1	BHI	24	5.77 ± 0.86^{cde}	[3.61, 7.93]	0.99	0.007
		120	2.43 ± 0.72^{abc}	[0.63, 4.23]	0.97	0.028
<i>C. freundii</i> ENTSE 1-3	M63	24	6.96 ± 1.16^{de}	[4.06, 9.85]	0.99	0.009
		120	3.64 ± 1.10^{abcd}	[0.88, 6.39]	0.97	0.030
<i>E. cloacae</i> ENTSE 8-1	M63	24	0.53 ± 0.45^a	[-0.59, 1.66]	0.82	0.179
		120	0.58 ± 0.53^a	[-0.73, 1.90]	0.80	0.197
<i>H. alvei</i> ENTSE 15-1	M63	24	1.43 ± 0.03^a	[1.35, 1.50]	0.99	< 0.001
		120	5.02 ± 0.49^{bcde}	[4.90, 5.14]	0.57	< 0.001
<i>M. morganii</i> SFTCBS1	M63	24	1.57 ± 0.56^{ab}	[0.18, 2.96]	0.96	0.040
		120	2.32 ± 0.16^{abc}	[1.92, 2.71]	0.99	0.002

Note: Values are expressed as means $\pm$ standard deviations (SDs) ($n = 3$). Superscript letters indicate significant differences ($p < 0.05$) determined by Tukey's HSD post hoc test, with shared letters indicating no significant difference. η_p^2 represents the partial eta squared (effect size).

Table 2. AuNP concentrations obtained from the four selected strains grown in the absence or presence of HAuCl_4 .

Bacterial Strain	HAuCl_4 Concentration	Reaction Incubation Time (h)	AuNP Concentration ($\mu\text{g/mL}$) from a Culture Grown in the Presence or Absence of HAuCl_4 (mean $\pm$ SD)	95% Confidence Interval (CI)	Effect Size (η_p^2)	p-value
<i>C. freundii</i> ENTSE 1-3	0 μM	24	40.25 ± 2.62^{cd}	[33.72, 46.77]	0.99	0.001
		120	58.25 ± 3.62^{gh}	[49.23, 67.26]	0.99	0.001
<i>E. cloacae</i> ENTSE 8-1	0 μM	24	57.69 ± 0.87^{fgh}	[55.52, 59.86]	0.99	< 0.001
		120	51.12 ± 0.65^e	[49.49, 52.74]	0.99	< 0.001
<i>H. alvei</i> ENTSE 15-1	0 μM	24	12.28 ± 0.87^a	[10.11, 14.46]	0.99	0.002
		120	29.68 ± 0.76^b	[27.79, 31.57]	0.99	< 0.001
<i>M. morganii</i> SFTCBS1	0 μM	24	78.56 ± 0.79^{ij}	[76.57, 80.54]	0.99	< 0.001
		120	72.64 ± 3.68^i	[63.49, 81.78]	0.99	0.001
<i>C. freundii</i> ENTSE 1-3	20 μM	24	54.97 ± 3.60^{fgh}	[46.01, 63.93]	0.99	0.001
		120	101.06 ± 5.37^k	[87.70, 114.42]	0.99	0.001
<i>E. cloacae</i> ENTSE 8-1	20 μM	24	71.52 ± 1.05^i	[68.90, 74.14]	0.99	< 0.001
		120	72.40 ± 1.44^i	[68.81, 75.99]	0.99	< 0.001
<i>H. alvei</i> ENTSE 15-1	20 μM	24	ND	ND	ND	ND
		120	ND	ND	ND	ND
<i>M. morganii</i> SFTCBS1	20 μM	24	59.44 ± 0.56^b	[58.04, 60.83]	0.99	< 0.001
		120	53.36 ± 3.14^{fg}	[45.53, 61.18]	0.99	0.001
<i>C. freundii</i> ENTSE 1-3	50 μM	24	34.61 ± 2.27^{bc}	[28.97, 40.25]	0.99	0.001
		120	50.08 ± 3.11^{ef}	[42.33, 57.82]	0.99	0.001
<i>E. cloacae</i> ENTSE 8-1	50 μM	24	54.08 ± 1.18^{fgh}	[51.12, 57.03]	0.99	< 0.001
		120	81.12 ± 2.08^j	[75.95, 86.30]	0.99	< 0.001
<i>H. alvei</i> ENTSE 15-1	50 μM	24	ND	ND	ND	ND
		120	ND	ND	ND	ND
<i>M. morganii</i> SFTCBS1	50 μM	24	44.56 ± 1.44^{de}	[40.98, 48.14]	0.99	< 0.001
		120	30.45 ± 2.73^b	[23.65, 37.24]	0.99	0.003

Note: Values are expressed as means $\pm$ standard deviations (SDs) ($n = 3$). Superscript letters indicate significant differences ($p < 0.05$) determined by Tukey's HSD post hoc test, with shared letters indicating no significant difference. η_p^2 represents the partial eta squared (effect size).

ND, not determined due to no bacterial growth.

To evaluate the effect of aeration, the inocula of selected strains were grown in Lennox LB at 37°C for 36 h under static and aerated conditions. The AuNP concentrations were determined, as mentioned earlier. The concentrations of AuNPs synthesized by all four strains grown under static and aerated conditions are presented in Table 3. Static conditions significantly promoted AuNP synthesis by all four strains at both reaction incubation times (24 h and 120 h).

To evaluate the effect of cultivation time, the inocula of selected strains were grown in Lennox LB at 37°C for five cultivation times under static conditions. The AuNP concentrations were determined, as mentioned earlier. The concentrations of AuNPs synthesized by all four strains grown for five cultivation times are presented in Table 4. The significantly highest AuNP concentrations from the four selected strains at various cultivation times were as follows: *C. freundii* ENTSE 1-3 (12-h-old cultures at an incubation time of 120 h); *E. cloacae* ENTSE 8-1 (36-h-old cultures at an incubation time of 24 h); *H. alvei*

ENTSE 15-1 (36-h-old cultures at an incubation time of 120 h); and *M. morganii* SFTCBS1 (36-h-old cultures at both incubation times).

To evaluate the effect of reaction incubation temperatures and times, the inocula of selected strains were grown in Lennox LB at 37°C for 36 h under static conditions. The AuNP concentrations were determined, as mentioned earlier, except that the reactions were performed at 10 combinations of incubation temperature and time. The AuNP concentrations obtained from reaction incubation temperatures and times are presented in Table 5. The significantly highest AuNP concentrations from the four selected strains at various reaction temperatures and times were as follows: *C. freundii* ENTSE 1-3 (37°C for 72 h and 120 h); *E. cloacae* ENTSE 8-1 (55°C for 72 h and 120 h); *H. alvei* ENTSE 15-1 (37°C for 72 h and 120 h as well as at 55°C for 24 h and 48 h); and *M. morganii* SFTCBS1 (55°C for 120 h). ANOVA summary outputs, including sums of squares, degrees of freedom (*df*), and *F*-statistics, are presented in Table 6.

Table 3. AuNP concentrations obtained from the four selected strains grown under static and aerated conditions.

Bacterial Strain	Condition	Reaction Incubation Time (h)	AuNP Concentration (µg/mL) from a Culture Grown Under Static or Aerated Conditions (mean ± SD)	95% Confidence interval (CI)	Effect Size (η_p^2)	p-value
<i>C. freundii</i> ENTSE 1-3	Static	24	38.76 ± 0.91 ^e	[36.49, 41.04]	0.99	< 0.001
		120	56.79 ± 0.15 ^g	[56.39, 57.18]	0.99	< 0.001
<i>E. cloacae</i> ENTSE 8-1	Static	24	57.70 ± 0.86 ^g	[55.56, 59.85]	0.99	< 0.001
		120	43.73 ± 0.33 ^f	[42.90, 44.56]	0.99	< 0.001
<i>H. alvei</i> ENTSE 15-1	Static	24	10.74 ± 1.60 ^b	[6.76, 14.72]	0.99	0.007
		120	29.85 ± 0.91 ^d	[27.58, 32.11]	0.99	< 0.001
<i>M. morganii</i> SFTCBS1	Static	24	78.56 ± 0.79 ^{hi}	[76.57, 80.54]	0.99	< 0.001
		120	75.33 ± 2.90 ^h	[68.10, 82.56]	0.99	< 0.001
<i>C. freundii</i> ENTSE 1-3	Aerated	24	1.36 ± 0.54 ^a	[0.00, 2.71]	0.95	0.050
		120	18.81 ± 0.27 ^c	[18.13, 19.48]	0.99	< 0.001
<i>E. cloacae</i> ENTSE 8-1	Aerated	24	2.16 ± 0.31 ^a	[1.37, 2.94]	0.99	0.007
		120	3.25 ± 0.34 ^a	[2.39, 4.11]	0.99	0.004
<i>H. alvei</i> ENTSE 15-1	Aerated	24	1.44 ± 0.85 ^a	[-0.68, 3.57]	0.89	0.100
		120	0.74 ± 0.32 ^a	[-0.06, 1.55]	0.94	0.058
<i>M. morganii</i> SFTCBS1	Aerated	24	1.36 ± 0.45 ^a	[0.24, 2.47]	0.96	0.035
		120	1.44 ± 0.18 ^a	[0.98, 1.89]	0.99	0.005

Note: Values are expressed as means ± standard deviations (SDs) (*n* = 3). Superscript letters indicate significant differences (*p* < 0.05) determined by Tukey's HSD post hoc test, with shared letters indicating no significant difference. η_p^2 represents the partial eta squared (effect size).

Table 4. AuNP concentrations obtained from the four selected strains grown for five cultivation times.

Bacterial Strain	Cultivation Time	Reaction Incubation Time (h)	AuNP Concentration ($\mu\text{g/mL}$) from a Culture Grown for a Cultivation Time (mean $\pm$ SD)	95% Confidence Interval (CI)	Effect Size (η_p^2)	p-value
<i>C. freundii</i> ENTSF 1-3	6 h	24	4.50 $\pm$ 0.47 ^{abc}	[3.32, 5.69]	0.99	0.004
		120	8.89 $\pm$ 0.47 ^{defg}	[7.70, 10.07]	0.99	0.001
<i>E. cloacae</i> ENTSF 8-1	6 h	24	8.33 $\pm$ 0.42 ^{cdefg}	[7.27, 9.39]	0.99	0.001
		120	4.92 $\pm$ 0.64 ^{ab}	[3.32, 6.51]	0.99	0.006
<i>H. alvei</i> ENTSF 15-1	6 h	24	4.40 $\pm$ 0.32 ^{bc}	[3.58, 5.21]	0.99	0.002
		120	1.32 $\pm$ 0.58 ^a	[-0.12, 2.76]	0.94	0.059
<i>M. organii</i> SFTCBS1	6 h	24	12.20 $\pm$ 0.12 ^g	[11.90, 12.51]	0.99	< 0.001
		120	10.52 $\pm$ 0.36 ^{ef}	[9.60, 11.43]	0.99	< 0.001
<i>C. freundii</i> ENTSF 1-3	12 h	24	44.72 $\pm$ 2.58 ⁿ	[38.28, 51.15]	0.99	0.001
		120	68.80 $\pm$ 0.47 ^s	[57.05, 80.54]	0.99	0.002
<i>E. cloacae</i> ENTSF 8-1	12 h	24	10.68 $\pm$ 0.82 ^{fg}	[8.64, 12.71]	0.99	0.002
		120	9.60 $\pm$ 1.25 ^{efg}	[6.48, 12.71]	0.99	0.006
<i>H. alvei</i> ENTSF 15-1	12 h	24	6.36 $\pm$ 1.39 ^{bode}	[2.90, 9.81]	0.98	0.016
		120	4.39 $\pm$ 0.84 ^{abc}	[2.29, 6.49]	0.98	0.012
<i>M. organii</i> SFTCBS1	12 h	24	24.04 $\pm$ 0.24 ^h	[23.63, 24.64]	0.99	< 0.001
		120	33.07 $\pm$ 0.12 ^k	[32.77, 33.37]	0.99	< 0.001
<i>C. freundii</i> ENTSF 1-3	24 h	24	38.65 $\pm$ 1.73 ^{lm}	[34.34, 42.96]	0.99	0.001
		120	61.83 $\pm$ 1.28 ^{qr}	[58.65, 65.02]	0.99	< 0.001
<i>E. cloacae</i> ENTSF 8-1	24 h	24	35.12 $\pm$ 0.19 ^{kl}	[34.64, 35.59]	0.99	< 0.001
		120	32.64 $\pm$ 0.16 ^j	[32.24, 33.03]	0.99	< 0.001
<i>H. alvei</i> ENTSF 15-1	24 h	24	9.03 $\pm$ 1.00 ^{defg}	[6.60, 11.57]	0.99	0.004
		120	6.65 $\pm$ 0.76 ^{bc}	[4.76, 8.54]	0.99	0.004
<i>M. organii</i> SFTCBS1	24 h	24	50.40 $\pm$ 0.55 ^o	[49.02, 51.78]	0.99	< 0.001
		120	62.16 $\pm$ 2.48 ^r	[56.00, 68.33]	0.99	0.001
<i>C. freundii</i> ENTSF 1-3	36 h	24	39.26 $\pm$ 1.45 ^{lm}	[35.64, 42.89]	0.99	< 0.001
		120	57.65 $\pm$ 1.37 ^{pq}	[54.25, 61.05]	0.99	< 0.001
<i>E. cloacae</i> ENTSF 8-1	36 h	24	57.60 $\pm$ 0.88 ^p	[55.41, 59.78]	0.99	< 0.001
		120	50.80 $\pm$ 0.31 ^o	[50.01, 51.58]	0.99	< 0.001
<i>H. alvei</i> ENTSF 15-1	36 h	24	11.09 $\pm$ 1.92 ^g	[6.30, 15.88]	0.98	0.010
		120	31.77 $\pm$ 0.35 ^{jk}	[30.88, 32.66]	0.99	< 0.001
<i>M. organii</i> SFTCBS1	36 h	24	73.98 $\pm$ 1.44 ^t	[70.39, 77.57]	0.99	< 0.001
		120	75.97 $\pm$ 1.52 ^t	[72.48, 79.76]	0.99	< 0.001
<i>C. freundii</i> ENTSF 1-3	48 h	24	5.07 $\pm$ 0.90 ^{abcd}	[2.81, 7.32]	0.98	0.010
		120	10.93 $\pm$ 0.98 ^g	[8.56, 13.30]	0.99	0.003
<i>E. cloacae</i> ENTSF 8-1	48 h	24	30.29 $\pm$ 0.36 ^{ij}	[29.39, 31.19]	0.99	< 0.001
		120	41.30 $\pm$ 0.39 ^{mn}	[40.32, 42.28]	0.99	< 0.001
<i>H. alvei</i> ENTSF 15-1	48 h	24	2.04 $\pm$ 0.68 ^a	[0.35, 3.72]	0.96	0.035
		120	2.77 $\pm$ 0.79 ^{ab}	[0.80, 4.74]	0.97	0.026
<i>M. organii</i> SFTCBS1	48 h	24	26.87 $\pm$ 0.24 ^{hi}	[26.26, 27.48]	0.99	< 0.001
		120	33.88 $\pm$ 0.24 ^k	[33.27, 34.48]	0.99	< 0.001

Note: Values are expressed as means $\pm$ standard deviations (SDs) ($n = 3$). Superscript letters indicate significant differences ($p < 0.05$) determined by Tukey's HSD post hoc test, with shared letters indicating no significant difference. η_p^2 represents the partial eta squared (effect size).

Table 5. AuNP concentrations obtained from the reactions performed at ten combinations of reaction incubation temperatures and times.

Bacterial Strain	Incubation Time	Incubation Temperature	AuNP Concentration (µg/mL) from a Reaction at an Incubation Temperature and Time (mean ± SD)	95% Confidence Interval (CI)	Effect Size (η_p^2)	p-value
<i>C. freundii</i> ENTsf 1-3	6 h	37°C	8.36 ± 0.31 ^{ab}	[7.59, 9.14]	0.99	< 0.001
		55°C	18.08 ± 0.20 ^{cd}	[17.58, 18.57]	0.99	< 0.001
<i>E. cloacae</i> ENTsf 8-1	6 h	37°C	18.64 ± 0.15 ^{cd}	[18.25, 19.02]	0.99	< 0.001
		55°C	25.96 ± 0.24 ^{efgh}	[25.35, 26.56]	0.99	< 0.001
<i>H. alvei</i> ENTsf 15-1	6 h	37°C	0.22 ± 0.35 ^a	[-0.66, 1.11]	0.61	0.388
		55°C	3.12 ± 0.48 ^b	[1.91, 4.32]	0.99	0.008
<i>M. morganii</i> SFTCBS1	6 h	37°C	18.14 ± 0.16 ^{cd}	[17.73, 18.56]	0.99	< 0.001
		55°C	27.33 ± 0.12 ^{efghi}	[27.02, 27.63]	0.99	< 0.001
<i>C. freundii</i> ENTsf 1-3	24 h	37°C	38.01 ± 0.26 ^k	[37.35, 38.67]	0.99	< 0.001
		55°C	21.08 ± 0.20 ^{def}	[20.58, 21.57]	0.99	< 0.001
<i>E. cloacae</i> ENTsf 8-1	24 h	37°C	54.26 ± 2.07 ^m	[49.12, 59.41]	0.99	< 0.001
		55°C	65.76 ± 1.11 ⁿ	[62.99, 68.52]	0.99	< 0.001
<i>H. alvei</i> ENTsf 15-1	24 h	37°C	11.08 ± 0.59 ^c	[9.60, 12.55]	0.99	0.001
		55°C	34.04 ± 0.31 ^{hij}	[33.26, 34.81]	0.99	< 0.001
<i>M. morganii</i> SFTCBS1	24 h	37°C	75.92 ± 0.87 ^o	[73.74, 78.09]	0.99	< 0.001
		55°C	101.28 ± 3.21 ^p	[93.30, 109.25]	0.99	< 0.001
<i>C. freundii</i> ENTsf 1-3	48 h	37°C	44.40 ± 1.83 ^{kl}	[39.83, 48.96]	0.99	0.001
		55°C	23.54 ± 0.52 ^{defg}	[22.23, 24.85]	0.99	< 0.001
<i>E. cloacae</i> ENTsf 8-1	48 h	37°C	57.14 ± 0.87 ^m	[54.96, 59.32]	0.99	< 0.001
		55°C	76.74 ± 1.27 ^o	[73.57, 79.91]	0.99	< 0.001
<i>H. alvei</i> ENTsf 15-1	48 h	37°C	20.07 ± 0.68 ^{de}	[18.36, 21.77]	0.99	< 0.001
		55°C	35.23 ± 0.15 ^{ij}	[34.89, 35.66]	0.99	0.001
<i>M. morganii</i> SFTCBS1	48 h	37°C	74.89 ± 4.88 ^o	[62.75, 87.03]	0.99	0.001
		55°C	112.80 ± 5.44 ^q	[99.28, 126.32]	0.99	< 0.001
<i>C. freundii</i> ENTsf 1-3	72 h	37°C	55.43 ± 1.04 ^m	[52.82, 58.04]	0.99	< 0.001
		55°C	24.42 ± 0.92 ^{defg}	[22.11, 26.73]	0.99	< 0.001
<i>E. cloacae</i> ENTsf 8-1	72 h	37°C	52.48 ± 2.17 ^{lm}	[47.07, 57.88]	0.99	0.001
		55°C	94.24 ± 4.15 ^p	[83.92, 104.55]	0.99	0.001
<i>H. alvei</i> ENTsf 15-1	72 h	37°C	29.17 ± 0.44 ^{ghi}	[28.07, 30.27]	0.99	< 0.001
		55°C	25.84 ± 0.53 ^{de}	[24.50, 27.17]	0.99	< 0.001
<i>M. morganii</i> SFTCBS1	72 h	37°C	74.40 ± 1.60 ^o	[70.41, 78.38]	0.99	< 0.001
		55°C	115.36 ± 5.28 ^q	[102.22, 128.49]	0.99	0.001
<i>C. freundii</i> ENTsf 1-3	120 h	37°C	58.00 ± 0.95 ^{mn}	[55.62, 60.38]	0.99	< 0.001
		55°C	25.64 ± 0.59 ^{defgh}	[24.16, 27.11]	0.99	< 0.001
<i>E. cloacae</i> ENTsf 8-1	120 h	37°C	50.47 ± 1.12 ^{lm}	[47.67, 53.28]	0.99	< 0.001
		55°C	98.20 ± 7.09 ^p	[80.57, 115.82]	0.99	0.002
<i>H. alvei</i> ENTsf 15-1	120 h	37°C	30.32 ± 0.51 ^{ghi}	[29.04, 31.61]	0.99	< 0.001
		55°C	7.62 ± 0.49 ^{ab}	[6.39, 8.86]	0.99	0.001
<i>M. morganii</i> SFTCBS1	120 h	37°C	78.02 ± 6.64 ^o	[61.53, 94.52]	0.99	0.002
		55°C	131.19 ± 6.08 ^r	[116.08, 146.30]	0.99	0.001

Note: Values are expressed as means ± standard deviations (SDs) ($n = 3$). Superscript letters indicate significant differences ($p < 0.05$) determined by Tukey's HSD post hoc test, with shared letters indicating no significant difference. η_p^2 represents the partial eta squared (effect size).

Table 6. Detailed statistical outputs of ANOVA.

Experiment/Source	Sum of Squares	Degrees of Freedom (df)	Mean Square	F-value	Sig. (p-value)
AuNP concentrations obtained from the strains grown in three culture media	44102.590	23	1917.504	1264.987	< 0.001
AuNP concentrations obtained from the strains grown in the absence and presence of H ₂ AuCl ₄	24401.450	19	1284.287	209.903	< 0.001
AuNP concentrations obtained from the strains grown under static and aerated conditions	36203.372	15	2413.558	2430.057	< 0.001
AuNP concentrations obtained from the strains grown for five cultivation times	61743.318	39	1583.162	977.074	< 0.001
AuNP concentrations obtained from the reactions performed at ten combinations of reaction incubation temperatures and times	134733.494	39	3454.705	516.956	< 0.001

4. DISCUSSION

All 49 strains capable of resisting at least 50 μM H₂AuCl₄ belonged to six genera: *Enterobacter* (27 strains), *Citrobacter* (ten strains), *Providencia* (six strains), *Klebsiella* (two strains), *Morganella* (two strains), and *Yersinia* (two strains). A threshold concentration for gold resistance in bacteria has yet to be precisely defined. Instead, the threshold concentration varies across bacterial species, environments, and types of gold compounds tested. Even though AuNPs are viewed as promising agents for the treatment of multidrug-resistant bacteria due to their ability to both directly combat bacteria and deliver antibiotics, many bacteria possess mechanisms to overcome the toxicity of gold and can survive at high concentrations of gold compounds [37]. Gold-resistant bacteria and the concentrations at which they resisted have been reported in earlier studies, such as *Acinetobacter* sp. (20 μM AuCl₃) [38], *Arthrobacter* sp. (10 μM AuCl₃), *Enterobacter* sp. (10 μM AuCl₃), *Pseudomonas* sp. (10 μM AuCl₃), *Serratia* sp. (50 μM AuCl₃), and *Stenotrophomonas* sp. (25 μM AuCl₃) [39]. The four enterobacterial strains that synthesized the highest AuNP concentrations within their respective genera were selected. The four selected strains, namely *C. freundii* ENTSE 1-3, *E. cloacae* ENTSE 8-1, *H. alvei* ENTSE 15-1, and *M. morganii* SFTCBS1, synthesized AuNPs with spherical to slightly polyhedral shapes and average sizes ranging from 22 to 28 nm. Other *Citrobacter* and *Enterobacter* strains have been reported to synthesize AuNPs with similar morphologies. The *C. freundii*-derived AuNPs were spherical and polydisperse, with a size range of 30–60 nm [40]. The *Enterobacter aerogenes*-derived AuNPs were spherical and monodisperse, with a size range of 4–6 nm [30]. Of the 105 strains used in this study, 63 were previously classified as silver resistant based on their ability to grow in the presence of AgNO₃ at a concentration exceeding 512 mg/L, and 22 synthesized silver nanoparticles (AgNPs) [41].

Statistical comparisons of AuNP concentrations were performed to determine the optimal culturing factors and reaction conditions for all four strains. Lennox LB medium and static conditions were the most suitable parameters,

eliciting significantly higher AuNP synthesis by all four strains, whereas the most suitable inducer concentrations, culture ages, and reaction conditions were strain dependent. Among the four selected strains, *M. morganii* SFTCBS1 performed best in AuNP synthesis under the optimized parameters. The rationale that Lennox LB medium and static conditions promote AuNP synthesis is supported by previous studies. Bacterial AuNP synthesis is driven by various enzymes and metabolites. Bacterial metabolites acting as reducing agents in AuNP synthesis include aromatic compounds (e.g. prodigiosin), lipopeptides (e.g. surfactin), peptides, amines, amides, carboxylic acids, esters, alkanes, alkynes, phenols, and phosphates [42], and these metabolites are abundant in LB medium [43]. Nitrate-dependent reductase, NADPH-dependent reductase, and lactate dehydrogenase are key enzymes involved in AuNP synthesis [44, 45]. A medium containing glucose, peptone, yeast extract, and potassium nitrate (KNO₃) at a specific ratio (1.5:1:0.35:0.35), whose composition is similar to that of Lennox LB medium, enhanced the nitrate-dependent reductase activity of *B. licheniformis*, thereby promoting the synthesis of AgNPs [46]. As nitrate reductase is negatively regulated by oxygen, anaerobic conditions and oxygen concentrations of 4% or lower were found to induce the synthesis of this enzyme, which was responsible for AgNP synthesis by *E. coli* [47–49]. The inducer H₂AuCl₄ affects AuNP synthesis by liberating Au³⁺ ions for reduction to Au⁰ [17]. While H₂AuCl₄ at concentrations of 0, 20, or 50 μM was most suitable for each strain in this study, 1 mM was the most suitable concentration for *B. subtilis*, *E. coli*, *L. acidophilus*, and *S. thermophilus* [9].

The effects of various parameters on AuNP synthesis have been determined in previous studies. The most promising parameters for AuNP synthesis by *L. odysseyi* included a ratio of H₂AuCl₄ to bacterial extract of 1:9, a reaction temperature of 75°C, a reaction pH of 9.0, a bacterial extract concentration of 10%, and an H₂AuCl₄ concentration of 1.0 mM [17]. Kikuchi *et al.* [24] attested that the ratio of bacterial cells to potassium gold (III) chloride (KAuCl₄) concentration was crucial to AuNP synthesis by *L. casei*. AuNP synthesis was inhibited by an

excess of either *L. casei* cells or KAuCl_4 . A combination of *L. casei* cells (1.0 g/L) and 0.25 mM KAuCl_4 yielded AuNPs with λ_{max} of 534 nm. Bacterial concentration influenced AuNP synthesis by *P. aeruginosa*, with 6×10^8 cells/mL being the most effective concentration. Reaction conditions, including pH, temperature, and time, influenced the size and λ_{max} of the *P. aeruginosa*-derived AuNPs. The reactions at 25°C for 48 h, 37°C for 24 h, and 42°C for 24 h yielded AuNPs with average sizes of 39.0, 26.0, and 36.7 nm, respectively [25].

The advantages of AuNP synthesis by the four selected strains were as follows: (1) A simple culture medium (Lennox LB) could be used for bacterial cultivation; (2) The maximum AuNP concentrations were achieved after short cultivation times (12–36 h); (3) AuNP synthesis was extracellular, thus offering easy and convenient product harvesting; (4) The synthesized AuNPs were stable and had narrow size distributions; (5) The reactions occurred within short periods; (6) Static conditions were preferred for bacterial cultivation, thus eliminating the requirement for aeration equipment and associated costs; (7) The reactions could occur at temperatures of 37°C and 55°C, thus eliminating the requirement for methods and apparatus designed for high or boiling temperatures; and (8) Condition optimization yielded the maximum AuNP concentrations of 101.06 ± 5.37 , 98.20 ± 7.09 , 35.23 ± 0.15 , and 131.19 ± 6.08 $\mu\text{g/mL}$ from *C. freundii* ENTSEF 1-3, *E. cloacae* ENTSEF 8-1, *H. alvei* ENTSEF 15-1, and *M. morgani* SFTCBS1, respectively.

In this study, the synergistic effects of various factors, including medium type, inducer concentration, aeration, culture age, and reaction conditions, were demonstrated. AuNP synthesis by the four selected strains provides novel and promising alternatives to those achieved using other bacterial strains. The gold resistance characteristics of the selected strains would facilitate their survival under high concentrations of gold compounds and contribute to a higher yield of the synthesized AuNPs. Faster reactions were obtained with the selected strains from four genera than with *Aeromonas*, *Arthrobacter*, *Comamonas*, *Elizabethkingia*, *Pseudomonas*, and *Streptomyces*, which required 48 to 120 h [50, 51]. Compared to various bacterial species that synthesized AuNPs with different shapes and sizes, the four enterobacterial species synthesized AuNPs with spherical to slightly polyhedral shapes and average sizes ranging from 22 to 28 nm. This AuNP morphology has ideal properties for drug delivery and photothermal therapy. These AuNPs exhibit significantly higher uptake in radiation therapy for cancer treatment than smaller AuNPs and significantly higher tumour extravasation than larger AuNPs. This AuNP morphology provides longer persistence in the bloodstream, more precise malignant cell internalization, and the highest concentration and permanence within the target cell, as well as excellent thermal stability and high photothermal conversion efficiency [4, 52–54].

The limitations of this study arise from the lack of the following information: (1) biological mechanisms supporting the effects of the examined parameters on

AuNP synthesis; (2) determination of the effects of parameters on AuNP morphology; (3) morphological control of the synthesized AuNPs across diverse enterobacterial genera; (4) determination of the thermal stability of enzymes responsible for AuNP synthesis; (5) scale-up and replicative efficiency; and (6) demonstration of the applications of the synthesized AuNPs.

CONCLUSION

Gold resistance and AuNP-synthesizing ability were found to be common characteristics among 105 seafood-associated enterobacterial strains. The four selected strains from different genera, namely *C. freundii* ENTSEF 1-3, *E. cloacae* ENTSEF 8-1, *H. alvei* ENTSEF 15-1, and *M. morgani* SFTCBS1, synthesized AuNPs with λ_{max} peaks at 540 nm, spherical to slightly polyhedral shapes, and average sizes ranging from 22 to 28 nm. This study determined the most suitable cultivation and reaction conditions to enhance the yields of AuNPs synthesized by these strains. AuNP synthesis by these enterobacterial strains confers many benefits and therefore holds potential for future applications.

AUTHORS' CONTRIBUTIONS

Both authors contributed equally to this article and share first authorship. P.N. and N. P. conceived and designed the study, performed the experiments, analyzed the data, and wrote the manuscript.

LIST OF ABBREVIATIONS

AuNPs	=	Gold Nanoparticles
BHI	=	Brain Heart Infusion
CFU	=	Colony Forming Unit
Lennox LB	=	Lennox Luria-Bertani
OD	=	Optical Density
SEM	=	Scanning Electron Microscopy

ETHICS APPROVAL AND CONSENT TO PARTICIPATE

Not applicable.

HUMAN AND ANIMAL RIGHTS

Not applicable.

CONSENT FOR PUBLICATION

Not applicable.

AVAILABILITY OF DATA AND MATERIALS

All data generated or analyzed during this study are provided in this published article.

FUNDING

This work was financially supported by the Silpakorn University Research, Innovation and Creativity Administration Office under Grant SURDI 60/01/20.

CONFLICT OF INTEREST

The authors declare no conflict of interest, financial or otherwise.

ACKNOWLEDGEMENTS

Declared none.

REFERENCES

- [1] Eker F, Akdaşçı E, Duman H, Bechelany M, Karav S. Gold nanoparticles in nanomedicine: Unique properties and therapeutic potential. *Nanomaterials* 2024; 14(22): 1854. <http://dx.doi.org/10.3390/nano14221854> PMID: 39591094
- [2] Hammami I, Alabdallah NM, jomaa AA, kamoun M. Gold nanoparticles: Synthesis properties and applications. *J King Saud Univ Sci* 2021; 33(7): 101560. <http://dx.doi.org/10.1016/j.jksus.2021.101560>
- [3] Hu X, Zhang Y, Ding T, Liu J, Zhao H. Multifunctional gold nanoparticles: A novel nanomaterial for various medical applications and biological activities. *Front Bioeng Biotechnol* 2020; 8: 990. <http://dx.doi.org/10.3389/fbioe.2020.00990> PMID: 32903562
- [4] Georgeous J, AlSawafth N, Abuwatfa WH, Hussein GA. Review of gold nanoparticles: Synthesis, properties, shapes, cellular uptake, targeting, release mechanisms and applications in drug delivery and therapy. *Pharmaceutics* 2024; 16(10): 1332. <http://dx.doi.org/10.3390/pharmaceutics16101332> PMID: 39458661
- [5] Subara D, Jaswir I. Gold nanoparticles: Synthesis and application for halal authentication in meat and meat products. *Int J Adv Sci Eng Inf Technol* 2018; 8(4-2): 1633-41. <http://dx.doi.org/10.18517/ijaseit.8.4-2.7055>
- [6] Aly Khalil AM, Saied E, Mekky AE, Saleh AM, Al Zoubi OM, Hashem AH. Green biosynthesis of bimetallic selenium-gold nanoparticles using *Pluchea indica* leaves and their biological applications. *Front Bioeng Biotechnol* 2024; 11: 1294170. <http://dx.doi.org/10.3389/fbioe.2023.1294170> PMID: 38274007
- [7] Bahmanyar Z, Mohammadi F, Gholami A, Khoshneviszadeh M. Effect of different physical factors on the synthesis of spherical gold nanoparticles towards cost-effective biomedical applications. *IET Nanobiotechnol* 2023; 17(1): 1-12. <http://dx.doi.org/10.1049/nbt2.12100> PMID: 36326590
- [8] Yazdani S, Daneshkhan A, Diwate A, et al. Model for gold nanoparticle synthesis: Effect of pH and reaction time. *ACS Omega* 2021; 6(26): 16847-53. <http://dx.doi.org/10.1021/acsomega.1c01418> PMID: 34250344
- [9] El-Shanshoury AER, Ebeid EZE, Elsilik SE, Mohamed SF, Ebeid ME. Biogenic synthesis of gold nanoparticles by bacteria and utilization of the chemical fabricated for diagnostic performance of viral hepatitis C virus-NS4. *Lett Appl NanoBioScience* 2020; 9(3): 1395-408. <http://dx.doi.org/10.33263/LIANBS93.13951408>
- [10] Amina SJ, Guo B. A review on the synthesis and functionalization of gold nanoparticles as a drug delivery vehicle. *Int J Nanomedicine* 2020; 15: 9823-57. <http://dx.doi.org/10.2147/IJN.S279094> PMID: 33324054
- [11] Abdulazeem L, Abd FG. Biosynthesis and characterization of gold nanoparticles by using local *Serratia* spp. isolate. *Int J Pharm Qual Assur* 2019; 10(3): 8-11. <http://dx.doi.org/10.25258/ijpqa.10.3.13>
- [12] Abdulazeem L, Abd FG. Optimization of gold nanoparticles synthesis from local isolate of *E. coli* and their activity as antibacterial. *AIP Conf Proc* 2022; 2398(1): 040003. <http://dx.doi.org/10.1063/5.0095231>
- [13] Al-khafaji MH, Hashim MH. The synergistic effect of biosynthesized gold nanoparticles with antibiotic against clinical isolates. *Magallat Markaz Buhut al-Tiqniyyat al-Ahya'iyyat* 2019; 13(1): 58-62. <http://dx.doi.org/10.24126/jobrc.2019.13.1.569>
- [14] Ho NR, Kondiah K, De Maayer P. Complete genome sequence of *Enterobacter xiangfangensis* Pb204, a South African strain capable of synthesizing gold nanoparticles. *Microbiol Resour Announc* 2018; 7(22): 10.1128/mra.01406-18. <http://dx.doi.org/10.1128/mra.01406-18> PMID: 30533853
- [15] Mendoza RM, Baybay ZK, Fernando LM, Montecillo AD, Ilag LL, Villegas LC. Characterization of gold nanoparticles produced by biogenic synthesis using *Serratia marcescens* NBL1001. *IOP Conf Ser Earth Environ Sci* 2019; 230: 012103. <http://dx.doi.org/10.1088/1755-1315/230/1/012103>
- [16] Prema P, Iniya PA, Immanuel G. Microbial mediated synthesis, characterization, antibacterial and synergistic effect of gold nanoparticles using *Klebsiella pneumoniae* (MTCC-4030). *RSC Advances* 2016; 6(6): 4601-7. <http://dx.doi.org/10.1039/C5RA23982F>
- [17] Cherian T, Maity D, Rajendra Kumar RT, et al. Green chemistry based gold nanoparticles synthesis using the marine bacterium *Lysinibacillus odyseeyi* PBCW2 and their multitudinous activities. *Nanomaterials* 2022; 12(17): 2940. <http://dx.doi.org/10.3390/nano12172940> PMID: 36079977
- [18] Huang BC, Yi YC, Chang JS, Ng IS. Mechanism study of photo-induced gold nanoparticles formation by *Shewanella oneidensis* MR-1. *Sci Rep* 2019; 9(1): 7589. <http://dx.doi.org/10.1038/s41598-019-44088-4> PMID: 31110216
- [19] Nadaf NY, Kanase SS. Biosynthesis of gold nanoparticles by *Bacillus marisflavi* and its potential in catalytic dye degradation. *Arab J Chem* 2019; 12(8): 4806-14. <http://dx.doi.org/10.1016/j.arabjc.2016.09.020>
- [20] Rajasekar T, Karthika K, Muralitharan G, et al. Green synthesis of gold nanoparticles using extracellular metabolites of fish gut microbes and their antimicrobial properties. *Braz J Microbiol* 2020; 51(3): 957-67. <http://dx.doi.org/10.1007/s42770-020-00263-8> PMID: 32424714
- [21] Shunmugam R, Renukadevi Balusamy S, Kumar V, Menon S, Lakshmi T, Perumalsamy H. Biosynthesis of gold nanoparticles using marine microbe (*Vibrio alginolyticus*) and its anticancer and antioxidant analysis. *J King Saud Univ Sci* 2021; 33(1): 101260. <http://dx.doi.org/10.1016/j.jksus.2020.101260>
- [22] Dinesh RA, Raja S, Kishanlal N, Nachiyar C V, Sunkar S. Microbe-based synthesis of gold nanoparticles and its catalytic applications. *Biosci Biotechnol Res Asia* 2023; 20(2): 511-27. <http://dx.doi.org/10.13005/bbra/3106>
- [23] Kuyukina MS, Makarova MV, Ivshina IB, Kazymov KP, Osovetsky BM. Biosynthesis and characterization of gold nanoparticles produced using *Rhodococcus actinobacteria* at elevated chloroauric acid concentrations. *Int J Mol Sci* 2022; 23(21): 12939. <http://dx.doi.org/10.3390/ijms232112939> PMID: 36361740
- [24] Kikuchi F, Kato Y, Furihata K, et al. Formation of gold nanoparticles by glycolipids of *Lactobacillus casei*. *Sci Rep* 2016; 6(1): 34626. <http://dx.doi.org/10.1038/srep34626> PMID: 27725710
- [25] Ahmady IM, Parambath JBM, Elsheikh EAE, et al. Bacterial synthesis of anisotropic gold nanoparticles. *Appl Microbiol Biotechnol* 2025; 109(1): 62. <http://dx.doi.org/10.1007/s00253-025-13438-w> PMID: 40064650
- [26] Cheng Y, Ke Z, Bian X, et al. Selective mineralization and recovery of Au (III) from multi-ionic aqueous systems by *Bacillus licheniformis* FZUL-63. *Minerals* 2019; 9(7): 392. <http://dx.doi.org/10.3390/min9070392>
- [27] El-Bendary MA, Afifi SS, Moharam ME, Elsoud MMA, Gawdat NA. Optimization of *Bacillus subtilis* NRC1 growth conditions using response surface methodology for sustainable biosynthesis of gold nanoparticles. *Sci Rep* 2022; 12(1): 20882. <http://dx.doi.org/10.1038/s41598-022-25324-w> PMID: 36463321
- [28] Satisha S, Syed B, Prasad NMN. Endogenic mediated synthesis of gold nanoparticles bearing bactericidal activity. *J Microsc Ultrastruct* 2016; 4(3): 162-6. <http://dx.doi.org/10.1016/j.jmau.2016.01.004> PMID: 30023223

- [29] Honary S, Gharaei-Fathabad E, Paji ZK, Eslamifar M. A novel biological synthesis of gold nanoparticle by *Enterobacteriaceae* family. Trop J Pharm Res 2013; 11(6): 887-91.
<http://dx.doi.org/10.4314/tjpr.v11i6.3>
- [30] Srinath BS, Rai RV. Biosynthesis of gold nanoparticles using extracellular molecules produced by *Enterobacter aerogenes* and their catalytic study. J Cluster Sci 2015; 26(5): 1483-94.
<http://dx.doi.org/10.1007/s10876-014-0835-9>
- [31] Nimnoi P, Pongsilp N. Distribution and expression of virulence genes in potentially pathogenic bacteria isolated from seafood in Thailand. CYTA J Food 2020; 18(1): 753-63.
<http://dx.doi.org/10.1080/19476337.2020.1842502>
- [32] Pongsilp N, Nimnoi P. Diversity and antibiotic resistance patterns of enterobacteria isolated from seafood in Thailand. CYTA J Food 2018; 16(1): 793-800.
<http://dx.doi.org/10.1080/19476337.2018.1479453>
- [33] Nimnoi P, Pongsilp N. Identification, characterization, and virulence gene expression of marine enterobacteria in the Upper Gulf of Thailand. Microorganisms 2022; 10(3): 511.
<http://dx.doi.org/10.3390/microorganisms10030511> PMID: 35336087
- [34] Schneider CA, Rasband WS, Eliceiri KW. NIH Image to ImageJ: 25 years of image analysis. Nat Methods 2012; 9(7): 671-5.
<http://dx.doi.org/10.1038/nmeth.2089> PMID: 22930834
- [35] Ezraty B, Henry C, Hérisse M, Denamur E, Barras F. Commercial Lysogeny Broth culture media and oxidative stress: A cautious tale. Free Radic Biol Med 2014; 74: 245-51.
<http://dx.doi.org/10.1016/j.freeradbiomed.2014.07.010> PMID: 25048972
- [36] Rewak-Soroczynska J, Dorotkiewicz-Jach A, Drulis-Kawa Z, Wiglusz RJ. Culture media composition influences the antibacterial effect of silver, cupric, and zinc ions against *Pseudomonas aeruginosa*. Biomolecules 2022; 12(7): 963.
<http://dx.doi.org/10.3390/biom12070963> PMID: 35883519
- [37] Saed M, Ayivi RD, Wei J, Obare SO. Gold nanoparticles antibacterial activity: Does the surface matter? Colloid Interface Sci Commun 2024; 62: 100804.
<http://dx.doi.org/10.1016/j.colcom.2024.100804>
- [38] Sanyal SK, Shuster J. Gold particle geomicrobiology: Using viable bacteria as a model for understanding microbe-mineral interactions. Mineral Mag 2021; 85(1): 117-24.
<http://dx.doi.org/10.1180/mgm.2021.19>
- [39] Sanyal SK, Reith F, Shuster J. A genomic perspective of metal-resistant bacteria from gold particles: Possible survival mechanisms during gold biogeochemical cycling. FEMS Microbiol Ecol 2020; 96(7): fiae111.
<http://dx.doi.org/10.1093/femsec/fiae111> PMID: 32495831
- [40] Hashim MH. Biosynthesis of gold nanoparticles by food origin *Citrobacter freundii*. Biochem Cell Arch 2018; 18(2): 1971-8.
- [41] Nimnoi P, Pongsilp N. Characterization of promising enterobacterial strains for silver nanoparticle synthesis and enhancement of product yields under optimal conditions. Open Agric 2025; 10(1): 20250472.
<http://dx.doi.org/10.1515/opag-2025-0472>
- [42] Nadeem M, Pervez L, Khan AM, et al. Microbial-mediated synthesis of gold nanoparticles—current insights and future vistas. Gold Bull 2023; 56(2): 69-81.
<http://dx.doi.org/10.1007/s13404-023-00335-1>
- [43] Wang H, Guo J, Chen X, He H. The metabolomics changes in Luria-Bertani broth medium under different sterilization methods and their effects on *Bacillus* growth. Metabolites 2023; 13(8): 958.
<http://dx.doi.org/10.3390/metabo13080958> PMID: 37623901
- [44] Dinh T, Dobó Z, Palotás ÁB, Kovács H. A review of gold nanoparticle synthesis: Transitioning from conventional techniques to plant-mediated green nanofabrication. Mater Today Chem 2025; 48: 103003.
<http://dx.doi.org/10.1016/j.mtchem.2025.103003>
- [45] Lyu N, Sun B, Tukova A, Zhang Q, Gu Z, Wang Y. *In situ* synthesis of gold nanoparticles on layered double hydroxide nanoparticles for multiplexing molecular imaging of single cells. Mater Today Chem 2023; 33: 101698.
<http://dx.doi.org/10.1016/j.mtchem.2023.101698>
- [46] Vaidyanathan R, Gopalram S, Kalishwaralal K, Deepak V, Pandian SRK, Gurunathan S. Enhanced silver nanoparticle synthesis by optimization of nitrate reductase activity. Colloids Surf B Biointerfaces 2010; 75(1): 335-41.
<http://dx.doi.org/10.1016/j.colsurfb.2009.09.006> PMID: 19796922
- [47] Kodashenas B. Nitrate reductase enzyme in *Escherichia coli* and its relationship with the synthesis of silver nanoparticles. UJRSET 2015; 3(1): 26-32.
- [48] Tiso M, Schechter AN. Nitrate reduction to nitrite, nitric oxide and ammonia by gut bacteria under physiological conditions. PLoS One 2015; 10(3): e0119712.
<http://dx.doi.org/10.1371/journal.pone.0119712> PMID: 25803049
- [49] Fischer M, Falke D, Pawlik T, Sawers RG. Oxygen-dependent control of respiratory nitrate reduction in mycelium of *Streptomyces coelicolor* A3(2). J Bacteriol 2014; 196(23): 4152-62.
<http://dx.doi.org/10.1128/JB.02202-14> PMID: 25225271
- [50] Ahmady IM, Parambath JBM, Elsheikh EAE, et al. Investigating soil and ATCC bacterial strains for their ability to synthesize anisotropic gold nanoparticles. Appl Microbiol Biotechnol 2026; 110(1): 22.
<http://dx.doi.org/10.1007/s00253-025-13689-7> PMID: 41526728
- [51] Dehnad A, Hamed J, Derakhshan-Khadivi F, Abusov R. Green synthesis of gold nanoparticles by a metal resistant *Arthrobacter nitroguajacolicus* isolated from gold mine. IEEE Trans Nanobiosci 2015; 14(4): 393-6.
<http://dx.doi.org/10.1109/TNB.2014.2377232> PMID: 25594974
- [52] Dung NT, Linh NTN, Chi DL, et al. Optical properties and stability of small hollow gold nanoparticles. RSC Advances 2021; 11(22): 13458-65.
<http://dx.doi.org/10.1039/D0RA09417J> PMID: 35423895
- [53] Medici S, Peana M, Coradduzza D, Zoroddu MA. Gold nanoparticles and cancer: Detection, diagnosis and therapy. Semin Cancer Biol 2021; 76: 27-37.
<http://dx.doi.org/10.1016/j.semcancer.2021.06.017> PMID: 34153434
- [54] Sah B, Antosh MP. Effect of size on gold nanoparticles in radiation therapy: Uptake and survival effects. J Nano Med 2019; 2(1): 1013.

DISCLAIMER: The above article has been published, as is, ahead-of-print, to provide early visibility but is not the final version. Major publication processes like copyediting, proofing, typesetting and further review are still to be done and may lead to changes in the final published version, if it is eventually published. All legal disclaimers that apply to the final published article also apply to this ahead-of-print version.